


TECHNOLÓG

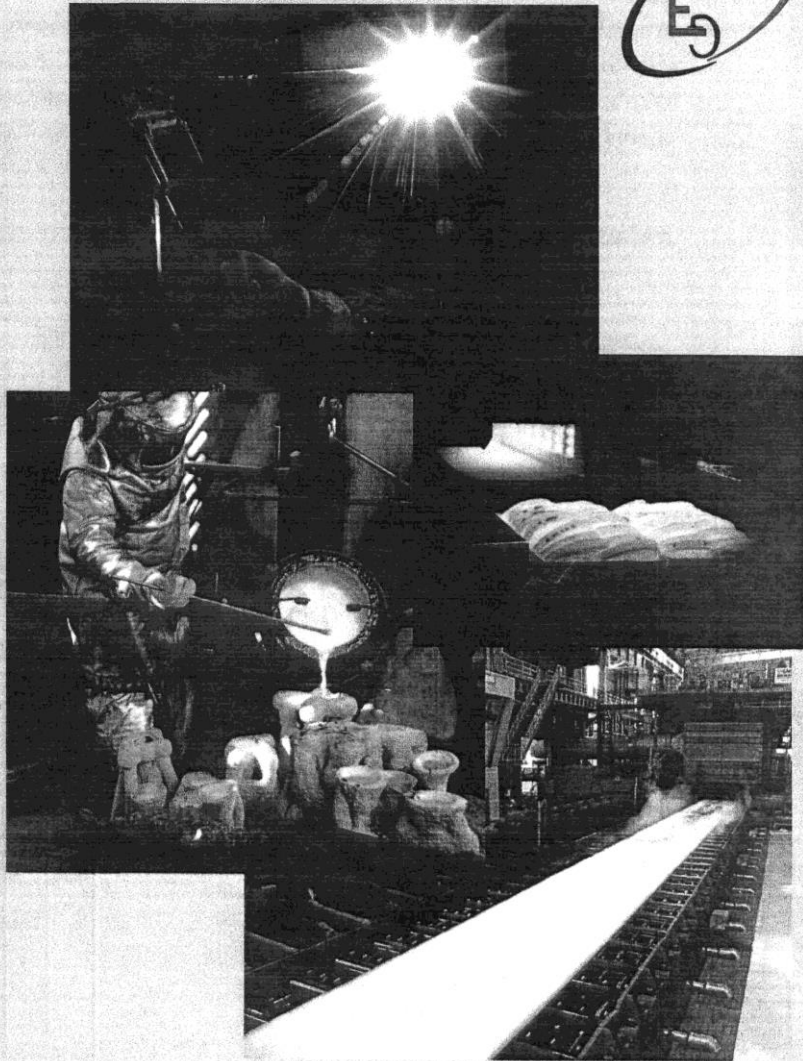

Ročník 5
číslo 3
jún 2013

ISSN 1337-8996

03/2013

TECHNOLÓG

Vychádza spravidla dvakrát ročne. Publikuje vedecké, výskumné, odborné, teoretické práce, návody, štúdiá, recenzie, informácie o spracovaní technických materiálov. Zameriava sa na uverejňovanie príspevkov a prác venujúcich sa otázkam z oblasti trieskových a beztrieskových technológií, fyzikálnych princípov nekonvenčných technológií, technologickosti konštrukcií nástrojov, ekonomike výrobného procesu, ekologizácii, spracovaniu odpadov. Takisto publikuje práce o strojoch, nástrojoch, prípravkoch a meracej technike pre oblasť mechanických technológií, výsledkoch výskumu vo sfére informačných technológií v technologickej oblasti. Uverejňuje práce o histórii a vývine mechanických technológií.

Časopis zverejňuje príspevky v jazykoch: slovenskom, českom, poľskom, ruskom, anglickom a nemeckom.

Všetky príspevky sú recenzované a redakcia si vyhradzuje právo na ich redakčnú úpravu. Nepreberá sa zodpovednosť za prípadné škody spôsobené použitím úkonov, metód, produktov, ideí, návodov a pod. publikovaných autormi príspevkov.

Evidenčné číslo MK SR-2800/08

ISSN 1337-8996

Adresa redakcie:

Žilinská univerzita v Žiline, Strojnícka fakulta, Univerzitná 1, 010 26 Žilina

Telefón: 041-513 2764, 513 2771,

Fax: 041-513 1535

e-mail: jan.moravec@fstroj.uniza.sk

Vydáva Žilinská univerzita v Žiline v EDIS-vydavateľstve ŽU

Univerzitná HB, 010 26 Žilina, IČO 00 397 563

šéfredaktor - editor in chief:
vedecký redaktor - scientific editor:

doc. Ing. Ján Moravec, PhD.
prof. Ing. Jozef Pilc, CSc.

redakčná rada - editorial board:

doc. Ing. Ján Moravec, PhD.	(SK)
prof. Ing. Jozef Pilc, CSc.	(SK)
prof. Ing. Karol Vasilko, DrSc.	(SK)
prof. Ing. Augustín Sládek, PhD.	(SK)
prof. Ing. Peter Demeč, CSc.	(SK)
prof. Ing. Jan Suchánek, CSc.	(CZ)
prof. Dr. Ing. Milan Sága	(SK)
prof. Dr. hab. Ing. Jurij Shalapko	(UA)
prof. Dr. Ing. Miroslav Neslušán	(SK)
prof. Ing. Danka Bolibruchová, PhD.	(SK)
doc. Ing. Marian Mikulík, PhD.	(SK)
Dipl. Ing. Eva Reger	(D)

OBRÓBKA LASEROWA PRZECIWZUŻYCIOWYCH POWŁOK ELEKTROISKROWYCH <i>Norbert Radek, Jozef Bronček, Jurij Shalapko</i>	181
WYMIANA CIEPŁA NA POWIERZCHNI MODYFIKOWANEJ ELEKTROISKROWO <i>Norbert Radek, Łukasz .J. Orman, Jozef Bronček</i>	185
TECHNOLOGIE PRO NEPRETRŽITOU VÝROBU ANORGANICKÝCH NANOVLÁKEN <i>Radovan Kovář</i>	189
MECHANICAL PROPERTIES OF NON-POLYURETHANE MATERIALS FOR PU FOAM REPLACEMENT IN CAR SET <i>Michal Petrů, Ondřej Novák, Petr Lepšík</i>	195
SLEDOVÁNÍ DILATACE SLITIN ZINKU PŘI JEJÍM TUHNUTÍ <i>Josef Vosáhlo</i>	201
ANALÝZA VPLYVU OPOTREBENIA NÁSTROJA PRI SÚSTRUŽENÍ NA DEFORMÁCIE LOŽISKOVÝCH KRÚŽKOV POMOCOU BARKAHOUSENOVHO ŠUMU <i>Jaroslav Dubec, Miroslav Neslušan, Miroslav Faktor</i>	207
MOŽNOSTI OPTIMALIZÁCIE ROZHODOVACIEHO PROCESU V RÁMCI NÁVRHU ZÁPUSTKOVÉHO KOVANIA <i>Jozef Kuba</i>	213
DISKRÉTNÁ OPTIMALIZÁCIA PARAMETROV TRAŤOVÉHO STROJA <i>Pavol Novák, Milan Uhříčik, Milan Sága</i>	217
VŘTANIE HLBOKÝCH OTVOROV VRTÁKMI TYPU HTS <i>Martin Letavay, Jozef Pilc</i>	223
THE MATERIAL TO OF THE ACTIVE COMPONENTS OF MOLDING TOOLS <i>Borislav Melo, Ján Moravec</i>	227
THREE-DIMENSIONAL S-N CURVE METHOD TO ESTIMATE FATIGUE LIFE OF ALUMINIUM ALLOY UNDER COMBINED LOADING AND COMPARING WITH FATIGUE CRITERIA <i>Peter Kopas, Milan Uhříčik, Milan Sága</i>	231
EFFECT OF SURFACE LAYERS OF STEEL WEAR RESISTANCE IN ABRASIVE MEDIUM <i>V. Gonchar, Jurij Shalapko, P. Kaplun, V. Kaplun</i>	235
VÝPOČTY A SIMULÁCIE PRI VÝVOJI KONŠTRUKCIÍ KOĽAJOVÝCH VOZIDIEL <i>Jozef Harušinec, Pavol Šťastniak, Ján Dižo</i>	239
POČÍTAČOVÁ ANALÝZA NÁKLADNÉHO VOZŇA VYBAVENÉHO PODVOZKAMI Y25 <i>Jozef Harušinec, Ján Dižo, Pavol Šťastniak</i>	245
DISKRÉTNÁ OPTIMALIZÁCIA PODVOZKU TRAŤOVÉHO STROJA S VYUŽITÍM MKP <i>Pavol Novák, Milan Uhříčik, Milan Sága</i>	251
ŠTÚDIUM MAGNETICKEJ ANIZOTROPIE PRI BRÚSENÍ A TVRDOM FRÉZOVANÍ <i>Tomáš Hrabovský, Zuzana Durstová, Miroslav Neslušan</i>	256

Vedecký výbor

prof. Ing. **Dana BOLIBRUCHOVÁ**, PhD. – predseda
doc. Ing. **Ján MORAVEC**, PhD. – výkonný predseda
prof. Dr. Ing. **Milan SÁGA**
prof. RNDr. **Peter BURY**, CSc.
prof. Ing. **Jozef MEŠKO**, PhD.
prof. Ing. **Peter DEMEČ**, CSc.
prof. Dr. Ing. **Miroslav NESLUŠAN**
prof. Dr. hab. Ing. **Jerzy SZALAPKO**
prof. Ing. **Augustín SLÁDEK**, PhD.
doc. Ing. **Martin ŽARNAY**, CSc.
doc. Ing. **Jozef BRONČEK**, PhD.
doc. Mgr. **Ivan MARTINČEK**, PhD.

Zoznam recenzentov príspevkov

Ing. **Ronald BAŠŤOVANSKÝ**, PhD.
Ing. **Miroslav BLATNICKÝ**, PhD.
Ing. **Martin BREZNIČAN**
prof. Ing. **Danka BOLIBRUCHOVÁ**, PhD.
doc. Ing. **Jozef BRONČEK**, PhD.
doc. Ing. **Vladimír DEKÝŠ**, PhD.
doc. Ing. **Peter FABIAN**, PhD.
Ing. **Michal HOLUBČÍK**
Ing. **Lenka HURTALOVÁ**, PhD.
prof. Dr. Ing. **Juraj GERLICI**
doc. Ing. **Daniel KÁČIK**, PhD.
Ing. **Peter KOPAS**, PhD.
doc. Mgr. **Ivan MARTINČEK**, PhD.
prof. Ing. **Anna MIČIETOVÁ**, PhD.
Ing. **Rudolf MINICH**, PhD.
doc. Ing. **Ján MORAVEC**, PhD.
doc. Ing. **Richard PASTIRČÁK**, PhD.
prof. Ing. **Jozef PILC**, CSc.
doc. Ing. **Dušan PUDIŠ**, PhD.
Ing. **Euboš ŠUŠLÍK**, PhD.
RNDr. **Viera ZATKALÍKOVÁ**, PhD.
doc. Ing. **Martin ŽARNAY**, CSc.

Effect of surface layers of steel wear resistance in abrasive medium

Gonchar, V.*

Khmelnitskiy National University
29016, Khmelnickiy,
st. Instyutaska 11
Ukraine
E-mail: vgkaplun@mail.ru

Shalapko, Yu. I.

Khmelnitskiy National University
29016, Khmelnickiy,
st. Instyutaska 11
Ukraine
E-mail: shalapko@yahoo.com

Kaplun, P.

Khmelnitskiy National University
29016, Khmelnickiy,
st. Instyutaska 11
Ukraine

Kaplun, V.

Khmelnitskiy National University
29016, Khmelnickiy,
st. Instyutaska 11
Ukraine

Abstract: The article highlights the results of experimental research of the impact of different structures of steels with different thermal (hardening for different temperatures) and chemical-thermal (carburizing, ion nitriding, nitrohardening) treatments for their wear resistance in abrasive medium that simulated conditions of the extruder running when manufacturing feed grain mixed fodder with the additives of mineral saponite.

To study the influence of the structure of the surface layers on their wear resistance the samples were made of different steels (Table 1), that were treated in various thermal and chemical-thermal conditions (hardening for different temperatures, ion nitriding, carburizing and nitrohardening). This made it is possible to obtain different structures of base materials (martensite, austenite) and the surface layers with carbide and nitride phases

The research was carried out on a special friction machine [1, 2] (Fig. 1) at the pressure of 4 MPa, sliding speed of 1.37 m/s and the temperature of 120-140 °C in model abrasive medium that simulated the conditions of the extruder running when manufacturing feed grain mixed fodder with saponite additives. Model abrasive medium was a water solution of flour with 10% of saponite. Saponite additive, containing more than 20 elements and microelements, significantly improves the livestock yield. Besides mineral saponite contains abrasive particles of quartz sand.

In the process of chemical-thermal treatment gradient hardening coatings are formed on the material surface. These coatings have different phases and negative hardness gradient in depth due to variable concentrations of diffusant and its compounds with the metal. Such compounds cause the changes in the structure of the material. Nitriding cause the generation of a solid solution of nitrogen in iron (α -phase, the concentration of nitrogen to 0.1%), which has lattice of bcc structure; solid solution based on compound Fe_4N (γ' -phase, the concentration of nitrogen to 6%) with face-centered lattice; solid solution based on nitrides $Fe_{2-3}N$ (ϵ -phase, the concentration of nitrogen to 11%), hexagonal lattice. ϵ -phase has a maximum hardness, high corrosion resistance, but it is very fragile. γ' -phase is characterized by lower hardness but higher ductility. α -phase has the lowest hardness. Alloying elements (Cr, Mo, W, Al, V, etc.) in the structure of the material increase the surface hardness of the material due to the formation of nitrides of alloying elements. The hardness of steel 6 is almost 2 times higher than of steel 2.

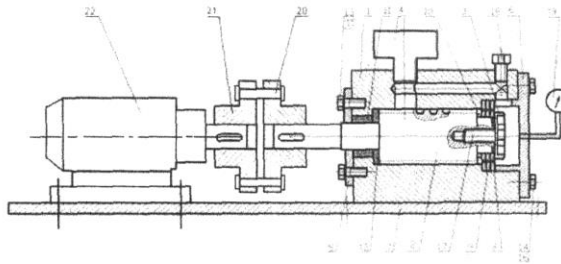


Fig. 1 Machine:

1 - trunk; 2 - shaft with sliced it turns screw, 3 - puck fixing samples 4 - tank with the model solution; 5-6 - trunk lid, 7 - base, 8-9 - samples, 10 - bush; 11-12 - bushings with antifriction material, 13-14 - screws fixation lids; 15-16 - washers, 17 - screw fixation of samples, 18 - adjusting screw of environment pressure; 19 - gauge, 20 - pin couplings, 21 - clutch, 22 - engine

Table 1
Chemical composition of steels under study

№	Steel grade	Chemical composition, %							
		C	Mn	Cr	Si	Ni	S	P	Cu
1	Steel 1	0.2	0.45	<0.25	0.2	<0.25	<0.04	<0.04	<0.25
2	Steel 2	0.45	0.6	<0.25	0.2	<0.25	<0.04	<0.035	<0.25
3	Steel 3	0.8	0.25	<0.2	0.25	<0.25	<0.028	<0.03	<0.25
4	Steel 4	0.98	0.3	1,5	0.25	<0.3	<0.02	<0.027	<0.25
5	Steel 5	2.1	0.35	12	0.2	<0.35	<0.03	<0.03	<0.3
6	Steel 6	0.4	0.5	1.45	0.3	<0.3	<0.025	<0.025	<0.3

Table 2
Characteristics of steel 5 after hardening

№	Hardening temperature T, °C	Surface microhardness H ₁₀₀ , MPa	Content of retained austenite A, %	Wear intensity I × 10 ⁻⁸ after the way 3 × 10 ³ M	Surface microhardness after friction way 3 × 10 ³ M
1	900	6900	19	1.65	7000
2	950	7090	28	1.37	7100
3	1000	7040	40	1.15	7090
4	1050	6700	55	1.1	6900
5	1100	5900	72	1.65	6300
6	1150	4800	93	2.6	4900

Table 2 and Fig. 2 show the results of the research of steel 5 properties (hardness, retained austenite and wear intensity) after hardening for different temperatures. Studies have shown that the hardness of the nitrided layer varies with the change of hardening temperature. The maximum hardness is achieved at 975 °C when its structure contains the maximum amount of martensite (44%), 36% of austenite and 20% of carbides. Decrease in hardness after hardening at temperatures below 975 °C is explained by the formation of soft ferrite component in the structure of material that is a part of troostite, which is characteristic for incomplete hardening of tool steels.

At a hardening temperature above 975 °C hardness also decreases, and this is explained the increases of retained austenite in its structure. The increase of hardening temperature increases the alloying of solid solution by chromium and carbon as a result of

carbide dissolution. As a result, steel has more retained austenite and less martensite. The hardness of steel is continuously decreasing and at hardening temperature above 1150 °C the structure of steel 5 contains 93% of retained austenite, 5% of carbides and 2% of martensite.

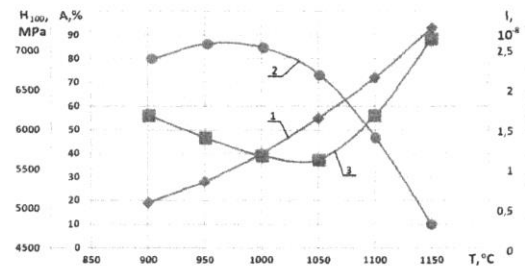


Fig. 2 Characteristics of steel 5 depending on hardening temperature: 1 - content of austenite A%; 2 - surface microhardness H₁₀₀, MPa, 3 - wear intensity I × 10⁻⁸

nitriding and its contents after nitriding does not exceed 10% (fig. 4 curve line 1). The structure of the material is almost stabilized due to the small number of metastable phases. The intensity of surface wear increases with the increase of steel hardening temperature that is explained by the decrease in the hardness of the material.

At nitrohardening, unlike nitriding, hardening with the increase of temperature the content of retained austenite increases significantly and at 1150 °C of hardening it is 91%. Maximum surface microhardness is 9050 MPa at 900 °C of hardening, that is 150 MPa lower than at nitriding. Surface microhardness decreases depending on the temperature of nitrohardening and on greater amount of austenite in the structure of the material. The minimum hardness at nitrohardening is 5600 MPa, that is 1.5 times less than at nitriding. This is explained by a large amount of retained austenite, that has low hardness and a minimum amount of martensite. The increase of the minimum surface hardness at nitrohardening to 800 MPa in comparison with the minimum hardness at hardening is explained by the content of oxide and nitride phases in the surface. Wear intensity at nitrohardening is much lower than at nitriding (fig. 4 curve lines 5, 6). Minimum wear intensity (0.3×10^{-8}) is achieved at 1030-1050 °C of hardening and 45-55% of retained austenite, that is 1.5 times less when compared with nitrided and 3.7 times less when compared with hardened steel 5. The regularity of influence of retained austenite on wear intensity of nitrohardened steel 5 is similar to the regularity of its wear during hardening, but differs in the fact that the velocity of wear intensity increase after hardening temperature of 1050 °C is lower because of alloying retained austenite by nitrogen, that increases its stability.

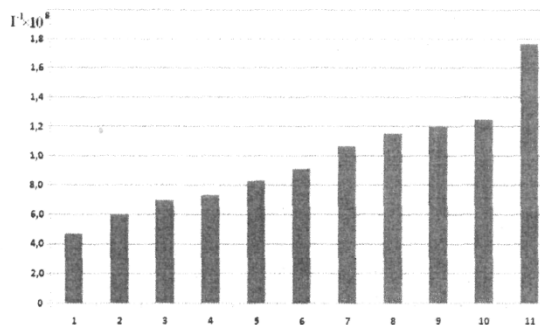


Fig. 5 Diagram of different steels wear at abrasive wear in model solutions with different thermal and chemical-thermal treatment: 1 – steel 1; 2 – steel 2 (hardening); 3 – steel 3 (hardening); 4 – steel 1 (carburizing); 5 – steel 4 (hardening); 6 – steel 5 (hardening); 7 – steel 2 (nitriding) 8 – steel 4 (nitriding); 9 – steel 6 (nitriding); 10 – steel 5 (nitriding); 11 – steel 5 (nitrohardening)

Fig. 5 shows the diagram of wear resistance indicator (I^{-1}) of various steels at abrasive wear in model solutions with different thermal and chemical-thermal treatment. The diagram shows that steel 5 has maximum wear resistance after nitrohardening, that is 3.7 times higher when compared with steel 20 without treatment, almost 2-3 times when compared with hardened steels, 2.4 times when compared with carburized steel 20 and 1.5 -1.7 times when compared with nitrided steels.

CONCLUSION

Thus, there is a linear dependence of wear resistance on hardness in abrasive medium for alloys with stable surface structure.

For alloys with unstable structure that are able to change under the influence of abrasive wear, it is necessary to take into consideration the structural state of the material surface and wear resistance depends mainly on the completeness of structural changes in the wear process.

LITERATURE

- [1] Patent 34233 Ukraine. Device for tests on corrosive and abrasive wear/ Kaplun V., Gonchar V. // №u2007 13431; applied 03.12.2007; published 11.08.2008, Builetin.№15.
- [2] GONCHAR V. (2008): *Methods of study of extruder's screw wear resistance for processing feed grain mixed fodder with saponite additives* // Problems of Tribology, -№4 -P. 19-21.
- [3] POPOV, V.: *Longevity of equipment for fire-resistant manufacturing* / V.S. Popov, N.N. Brikov, N.S. Dmitrichenko, P.G.Pristupa// «Metalurgija».- 1978.-232 p.
- [4] KITTEL, Ch. (1963) : *Introduction to solid-state physics*. 2-nd edition.- M., Fizmatgiz, – 696p.
- [5] CHALMERS, B. (1963): *Physical metallurgy*. - M., Metalurgizdat, 455p.